

UNCLASSIFIED

AD NUMBER

ADB026153

LIMITATION CHANGES

TO:

Approved for public release; distribution is unlimited.

FROM:

Distribution authorized to U.S. Gov't. agencies only; Test and Evaluation; FEB 1978. Other requests shall be referred to Army Armament Research and Development Command, Aberdeen Proving Ground, MD.

AUTHORITY

EA ltr 12 Sep 1978

THIS PAGE IS UNCLASSIFIED

THIS REPORT HAS BEEN DELIMITED
AND CLEARED FOR PUBLIC RELEASE
UNDER DOD DIRECTIVE 5200.20 AND
NO RESTRICTIONS ARE IMPOSED UPON
ITS USE AND DISCLOSURE.

DISTRIBUTION STATEMENT A

APPROVED FOR PUBLIC RELEASE;
DISTRIBUTION UNLIMITED.

AD B026153

AD-E400 120

AD

CONTRACTOR REPORT ARCSL-CR-78002

(2)
B.S.

FRICION STIMULI STUDIES IN BLENDING OPERATIONS


by

F. L. McIntyre

and

G. L. McKown

February 1978

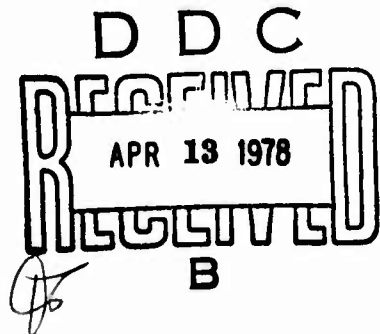

NASA NATIONAL SPACE TECHNOLOGY LABORATORIES
Computer Sciences Corporation
Engineering and Science Services Laboratory
NSTL Station, Mississippi 39529

Contract No. NAS13-50



US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND
Chemical Systems Laboratory
Aberdeen Proving Ground, Maryland 21010

Distribution limited to U. S. Government agencies only because of test and evaluation;
February 1978. Other requests for this document must be referred to Director, Chemi-
cal Systems Laboratory, Attn: DRSAR-CLJ-R, Aberdeen Proving Ground, MD 21010.

Disclaimer

The findings in this report are not to be construed as an official Department of the Army position, unless so designated by other authorized documents.

Disposition

Destroy this report when it is no longer needed. Do not return it to the originator.

UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER ARCSL-CR-78002	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) 6 FRICTION STIMULI STUDIES IN BLENDING OPERATIONS	5. TYPE OF REPORT OR SERIES COVERED 9 Final rept. Nov 76 - Apr 77	6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) 10 F. L. McIntyre G. L. McKown	8. CONTRACT OR GRANT NUMBER(s) 15 NAS13-50 MIPR 8100104001F4W5	9. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS PEMA LYN-D-1 Project 5761313
9. PERFORMING ORGANIZATION NAME AND ADDRESS NASA National Space Technology Laboratories Computer Sciences Corporation Engineering and Science Services Laboratory Bay St. Louis, Mississippi 39529	10. CONTROLLING OFFICE NAME AND ADDRESS 11 Chemical Systems Laboratory Attn: DRDAR-CLJ-R Aberdeen Proving Ground, Maryland 21010	11. REPORT DATE 12 Feb 78
11. CONTROLLING OFFICE NAME AND ADDRESS Chemical Systems Laboratory Attn: DRDAR-CLJ-R Aberdeen Proving Ground, Maryland 21010	12. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) Director, Chemical Systems Laboratory Attn: DRDAR-CLN-S Aberdeen Proving Ground, Maryland 21010 CPO - R. Belmonte 671-3402	13. NUMBER OF PAGES 14 17 17 p.
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) Director, Chemical Systems Laboratory Attn: DRDAR-CLN-S Aberdeen Proving Ground, Maryland 21010 CPO - R. Belmonte 671-3402	15. SECURITY CLASS. (of this report) UNCLASSIFIED	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE NA
16. DISTRIBUTION STATEMENT (of this Report) Distribution limited to U. S. Government agencies only because of test and evaluation; February 1978. Other requests for this document must be referred to Director, Chemi- cal Systems Laboratory, Attn: DRDAR-CLJ-R, Aberdeen Proving Ground, Maryland 21010.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Friction Stimulus Blending Colored Smokes		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Tests were performed on various pyromixes to determine friction stimuli due to the inducement of foreign objects and metal-to-metal contact during in-process blending. The test results indicated that the frictional energy required to ignite the pyrotechnic compositions was greater than those generated in these experiments. The initiation of pyrotechnics by friction during blending processes may be less hazardous than previously postulated based on reported incidents and accidents.		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

409 8841

PREFACE

The investigation described in this report was authorized under MIPR 8166104601F4W5, Project 5761313. This work was performed at the NASA National Space Technology Laboratories (NSTL) under the direction of the ARRADCOM Resident Operations Office through NASA by the Computer Sciences Corporation as the support contractor. The experimental work was completed April 1977. (It was begun in November 1976.)

Reproduction of this document in whole or in part is prohibited except with permission of the Director, Chemical Systems Laboratory, Attn: DRDAR-CLJ-R, Aberdeen Proving Ground, Maryland 21010. However, DDC is authorized to reproduce the document for United States Government purposes.

The use of trade names in this report does not constitute an official endorsement or approval of the use of such commercial hardware or software. This report may not be cited for purposes of advertisement.

The information in this document has not been cleared for release to the general public.

ACKNOWLEDGEMENT

The authors acknowledge the technical assistance of the Computer Sciences Corporation field crew; specifically, Messrs. S. Fuentes and H. D. Stove.

ACCESSION for	
NTIS	White Section <input type="checkbox"/>
DDC	Buff Section <input checked="" type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION _____	
BY _____	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	AVAIL. and/or SPECIAL
B	

TABLE OF CONTENTS

<u>Paragraph</u>		<u>Page</u>
1.0	INTRODUCTION	7
1.1	Objective	7
1.2	Authority	7
1.3	Background	7
2.0	EXPERIMENTAL METHODS	7
2.1	Test Configuration	7
2.2	Test Materials	10
3.0	RESULTS AND DISCUSSION	10
3.1	Ball Mill	10
3.2	Planetary Mixer	10
4.0	CONCLUSIONS	12
	RECOMMENDATIONS	12
	DISTRIBUTION LIST	13

LIST OF TABLES

<u>Table No.</u>	<u>Title</u>	<u>Page</u>
1	Test Results of Tumble Blending in Ball Mill With Various Pyrotechnic-Composition-Inducing Friction Stimuli	11
2	Test Results of Metal-to-Metal Contact Blending Various Pyrotechnic Compositions in a Planetary Blender	11

LIST OF ILLUSTRATIONS

<u>Figure No.</u>	<u>Title</u>	<u>Page</u>
1	Typical Test Apparatus Used in Experiments	8
2	Ball Mill Container Configurations	9
3	Typical Type of Foreign Objects Used in These Experiments	9

FRICITION STIMULI STUDIES IN BLENDING OPERATIONS

1.0 INTRODUCTION

1.1 Objective. The objective of this study was to determine whether sufficient frictional energy is available from foreign objects or metal to metal contact to stimulate initiation of various colored smoke compositions during in-process blending.

1.2 Authority. The work described in this report was authorized by MIPR 8166104601F4W 5 from Edgewood Arsenal to the National Space Technology Laboratories.

1.3 Background. Frictional stimulus has been a suspected source of initiation during the mixing cycle for most types of mixers used in the manufacture of pyrotechnic compositions. Specific types of mixers (e.g., helicone, planetary, ball mills, roller mills double arm, and vertical mixers) inherently have the potential to create friction due to internal moving parts. Other types of mixers (e.g., double cone, jet air mix and static blenders) which have no internal moving parts still are known to have initiated due to foreign objects being introduced into the mixers.


The ARRADCOM Resident Operations Office requested that testing be performed to evaluate the effects of friction due to the introduction of foreign objects into mixers and due to metal-metal contact in the moving parts of several blender configurations.

2.0 EXPERIMENTAL METHODS


2.1 Test Configuration. Two types of mixing actions were investigated in this study. Figures 1a and 1b show the typical test apparatus used in these experiments.

The first series of experiments were conducted in a 2.5-liter (0.66-gallon) light-metal tumble mill specifically developed by NSTL for these tests. Three types of ball mill containers were used: (1) type "A" which was a standard 2.5-liter (0.66-gallon) container with smooth inside surfaces, (2) type "B" which had 3.5-centimeter (2-inch) wide by 12.7-centimeter (5-inch) long strips of number-80 grit emery cloth glued to the interior of the can approximately 120 degrees apart and, (3) type "C" had two 1.9-cm by 1.9-cm (3/4-in. by 3/4-in.) angle iron strips tack-welded to the inside on opposite sides of the container. Figure 2, parts a, b, and c, show the modifications to the ball mill containers.

Figure 3 shows the typical types of foreign objects used in these experiments. Container "A" had 8 to 10 various size rocks; container "B" had nails, drill bits, nuts and bolts; and container "C" had flint and small pieces of metal bar stock. The containers were then filled approximately one-half full with 500 grams of a preblended pyromix or of components and tumbled for 30 minutes at 30 rpm. The ball mill was stopped and the rotation speed was reduced to 15 rpm and tumbled for an additional 30 minutes. Each pyrotechnic composition was tested in each container for a minimum of three trials.

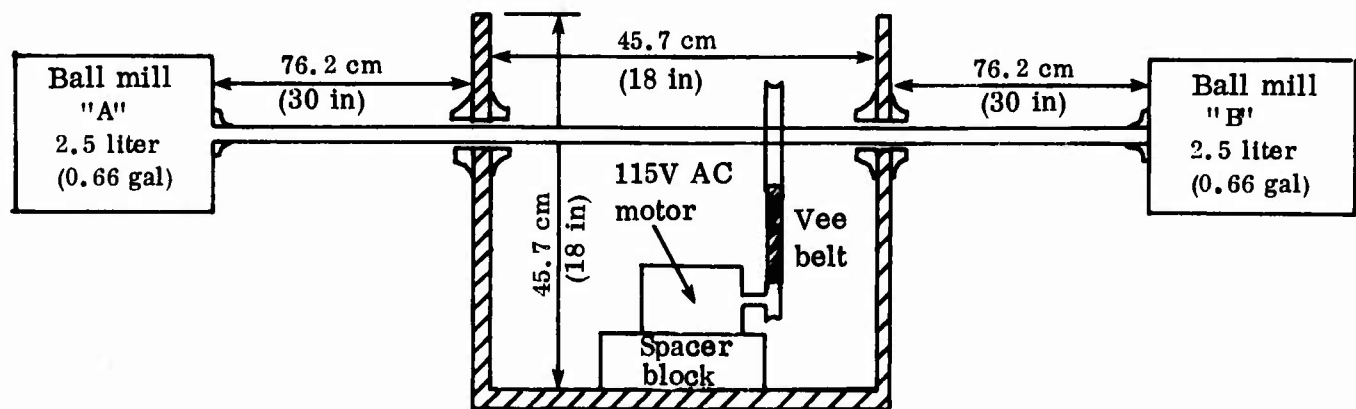

Tumble Mill Blender Test Configuration

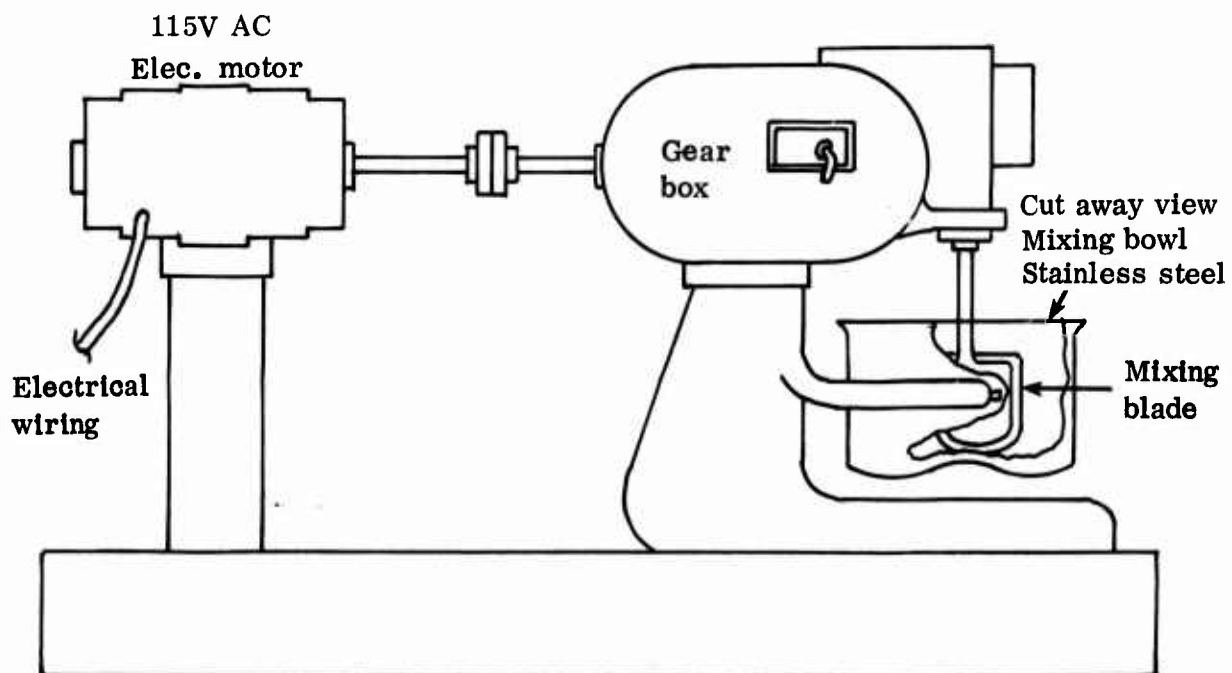

Model N-50-G Hobart Mixer

Figure 1. Typical Test Apparatus Used in Experiments

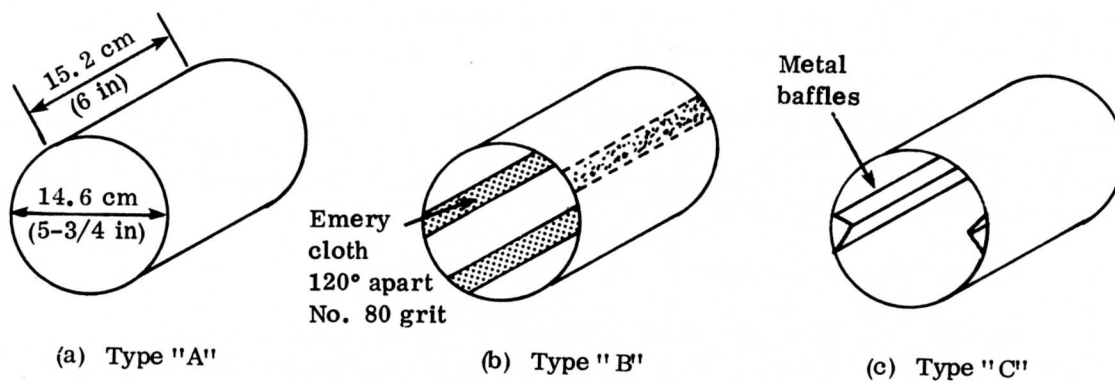


Figure 2. Ball Mill Container Configurations

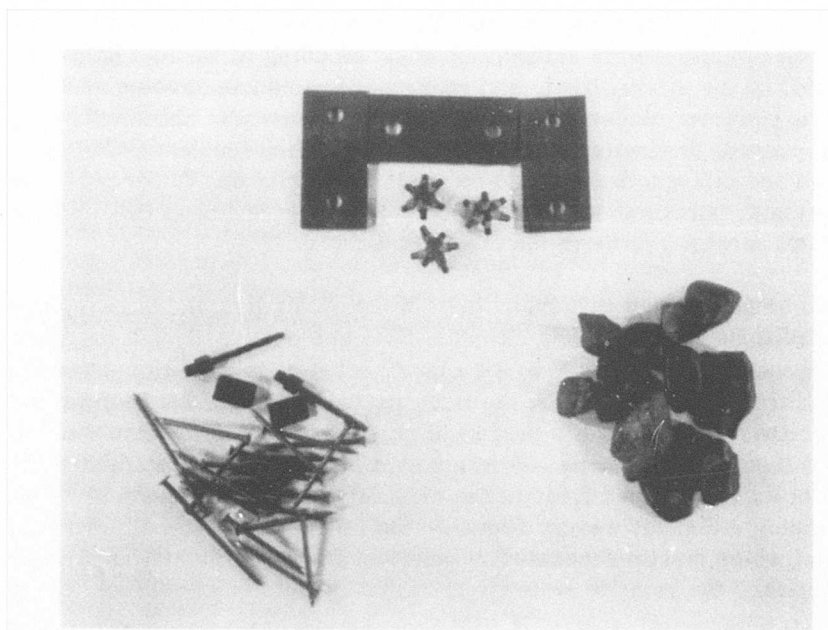


Figure 3. Typical Types of Foreign Objects Used in These Experiments

The second series of tests were conducted in a Model N-50-G Hobart planetary mixer. The mixing bowl was shimmed so that there was metal-to-metal contact between the bowl and the mixing blade. The bowl was filled with 500 grams of pyromix and blended for 30 minutes. Each test was conducted a minimum of three times.

2.2 Test Materials. Preblended sulphur and lactose based colored smokes were used initially in these experiments. Additionally four batches each of Violet Smoke Mix IV dry blend and an illuminant mix consisting of 45 percent magnesium/55 percent sodium nitrate were mixed in the ball mill and planetary mixer.

3.0 RESULTS AND DISCUSSION

3.1 Ball Mill. The tabulated results from these tests are shown in table 1. In no case was there an initiation observed either from friction caused by foreign objects being induced into the mixer or by deliberate roughening of the container walls. These negative results indicated that the frictional forces were insufficient to cause initiation due to either intergranular or granular object-container wall-intergranular effects. Small and King⁽¹⁾ have reported that an important consideration in determining whether frictional effect can cause ignition is if the material (in this case pyromix) melts before ignition. If this is the case then the melted material acts as a lubricant and lowers the coefficient of friction. In these tests the pyromix apparently acted as a lubricant, even though melting of the material or components was not obvious.

3.2 Planetary Mixer. The tabulated results are shown in table 2. The actual mixing process in a planetary blender is accomplished by kneading of the mix between the mixing blade and the side of the mixing bowl, and frictional forces can develop at any point between the mixing bowl and blade. In these tests the system was shimmed so that there was metal-to-metal contact to simulate the worst case condition for process blending. There was no initiation and this was believed to be again primarily due to the pyrotechnic material acting as a lubricant. In some cases the fit between blade and bowl was sufficiently tight to cause scoring and scratch marks in the mixer bowl.

It should be pointed out that these tests were qualitative and cursory in nature and were not intended to be a definitive treatment of the subject. Although the various pyrotechnic compositions were subjected to simulated worst case conditions, they failed to ignite. This failure may be caused by the inability to reproduce the head pressure of the pyromix in the mixer and the kinetic energy of objects falling more than 2 meters as might be expected in full-scale operations. Friction as a stimulus has been determined to be a common cause of explosions and fires in the manufacture of pyrotechnics⁽²⁾, but the results of these tests indicate that the energy required for initiation of typical pyromixes may be greater than that which can be generated in small-scale experimental apparatus. It would be valuable to determine the relative sensitivity of pyrotechnic compositions to various frictional

(1) Small T. and P. V. King, General Electric, Pyrotechnic Hazards Classification and Evaluation Program Contract NAS8-23523, Phase II, Segment 3, Final Report. Test Plan for Determining Hazard Associated with Pyrotechnic Manufacturing Processes, January 1971.

(2) McIntyre, F. L., General Electric, Final Report, Incident/Accident Survey (1950 through 1974). EM-CR-76011, December 1975.

Table 1. TEST RESULTS OF TUMBLE BLENDING IN BALL MILL WITH VARIOUS PYROTECHNIC-COMPOSITION-INDUCING FRICTION STIMULI

Test material	No. of tests	Selected rpm	Ball Mill container "A"	Ball Mill container "B"	Ball Mill container "C"
40-mm Red Smoke, lactose based batch No. 6349-2	3	30	NR	NR	NR
		15	NR	NR	NR
40-mm Red Smoke, lactose based batch No. 6310-2	3	30	NR	NR	NR
		15	NR	NR	NR
40-mm Green Smoke, lactose based, batch No. 6345-1	3	30	NR	NR	NR
		15	NR	NR	NR
40-mm Green Smoke, lactose based, batch No. 6289-1	3	30	NR	NR	NR
		15	NR	NR	NR
M-18 Green Smoke, sulfur based batch No. 6348-1	3	30	NR	NR	NR
		15	NR	NR	NR
M-18 Green Smoke, sulfur based batch No. 6316-2	3	30	NR	NR	NR
		15	NR	NR	NR
M-18 Violet Smoke, sulfur based batch No. 6349-1	3	30	NR	NR	NR
		15	NR	NR	NR
M-18 Violet Smoke, sulfur based batch No. 6307-1	3	30	NR	NR	NR
		15	NR	NR	NR
NSTL Illuminant Mix batch No. 1607-1	3	30	NR	NR	NR
		15	NR	NR	NR
M-18 Violet Smoke, sulfur based batch NSTL 1607-1	3	30	NR	NR	NR
		15	NR	NR	NR

NR = No Reaction

Table 2. TEST RESULTS OF METAL-TO-METAL CONTACT BLENDING VARIOUS PYROTECHNIC COMPOSITIONS IN A PLANETARY BLENDER

Test material	Number of tests	Results
40-mm Red Smoke, lactose based batch No. 6349-2	3	No Reaction
40-mm Red Smoke, lactose based batch No. 6310-2	3	No Reaction
40-mm Green Smoke, lactose based batch No. 6345-1	3	No Reaction
40-mm Green Smoke, lactose based batch No. 6389-2	3	No Reaction
M-18 Green Smoke, sulfur based batch No. 6348-1	3	No Reaction
M-18 Green Smoke, sulfur based batch No. 6316-2	3	No Reaction
M-18 Violet Smoke, sulfur based batch No. 6349-1	3	No Reaction
M-18 Violet Smoke, sulfur based batch No. 6307-1	3	No Reaction
NSTL Illuminant Mix batch No. 1607-1	3	No Reaction
M-18 Violet Smoke, sulfur based batch No. NSTL 1607-2	3	No Reaction

stimuli in mixing equipment. Such a determination would be useful in evaluating specific manufacturing mixing equipment regarding the potential for initiating pyrotechnic compositions by friction.

4.0 CONCLUSIONS

- (1) The frictional energy required to ignite the pyrotechnic materials tested is greater than that produced in these experiments.
- (2) The initiation of pyrotechnic materials by friction during blending process may be less hazardous than would be postulated based on reported incidents and accidents.

5.0 RECOMMENDATIONS

The failure to simulate known pyrotechnic incidents caused by friction warrants quantitative testing on particular pyromixes for a given manufacturing process to establish the relative sensitivity of the particular pyromix to various types of frictional stimuli.

**PYROTECHNIC HAZARDS REPORTS
DISTRIBUTION LIST**

<u>Addressee</u>	<u>No. of Copies</u>
Commander US Army Armament Research and Development Command Attn: DRDAR-LCM Dover, NJ 07801	1
Commander Pine Bluff Arsenal Attn: Safety Office Engineering and Technology Pine Bluff, AR 71601	1 1
Commander Frankford Arsenal Attn: Safety Office Bridge and Tacony Streets Philadelphia, PA 19137	1
Commander Rocky Mountain Arsenal Attn: Safety Office Denver, CO 80240	1
Director National Aeronautics and Space Administration Attn: Safety Office Washington, DC 20546	1
Director NASA National Space Technology Laboratories Attn: Safety Office Bay St. Louis, MS 39529	1
Chairman Department of Defense Explosives Safety Board Forrestal Building, GB-270 Washington, DC 20314	1
Commander US Army Materiel Development and Readiness Command Attn: Safety Office 5001 Eisenhower Avenue Alexandria, VA 22333	2

Project Manager, Munitions Production Base Modernization and Expansion Attn: DRCPM-PBM-E/Mr. Dybacki USA Materiel Development and Readiness Command Dover, NJ 07801	1
Director US Army Ballistics Research Laboratories Attn: Safety Office Aberdeen Proving Ground, MD 21005	1
Director Defense Research & Engineering Pentagon Washington, DC 20310	1
Administrator Defense Documentation Center Attn: Accessions Division Cameron Station Alexandria, VA 22314	2
Commander Chemical Systems Laboratory Attn: DRDAR-CLF DRDAR-CLN Aberdeen Proving Ground, MD 21010	1 3
Commander Aberdeen Proving Ground Attn: DRSAR-MAS-C Aberdeen Proving Ground, MD 21010	1 5
Commander US Army Armament Readiness Command Attn: DRSAR-IRC-E/Mr. Khwaja Rock Island, IL 61201	2
Director, Chemical Systems Laboratory Attn: DRDAR-CLJ-L Attn: DRDAR-CLJ-R Aberdeen Proving Ground, MD 21010	3 2
Commander US Army Armament Research and Development Command Attn: DRDAR-TSS Dover, NJ 07801	2